

Wall Construction

STYROFOAM Brand Insulation in Brick and Block Cavity Walls

Which Insulation Should I Specify: STYROFOAM or Polyisocyanurate

The above question is often asked by architects and specification writers. With all the widely varying claims by manufacturers regarding R-value, moisture resistance, reflective surfaces, etc., etc., there doesn't seem to be a good way to make an "apples to apples" comparison between the two products. One has a higher literature R-value, but the other has better moisture resistance and a warranted R-value. When considering a cavity insulation, which property is the most important?


Insulations Must be Moisture Resistant

Without a doubt, the most important property of an insulation in a brick/block wall cavity is **moisture resistance**. Why? If the insulation gets wet, it loses R-value and can no longer provide insulating value to the wall. It doesn't matter what its literature or initial R-value is, if it can't resist moisture, it won't maintain its R-value.

Wall Cavity is a Wet Environment

Will there be moisture present in the wall cavity? Well, consider the fact that the basic design premise of a brick veneer wall cavity is not to prevent moisture from entering the wall cavity, but rather to accommodate the moisture once it has entered the cavity. As one publication states, these walls are designed so that,

"rain water penetrating the facing wythe [brick veneer] of the wall drains into a cavity and can be conducted back to the exterior by suitable flashings and openings."

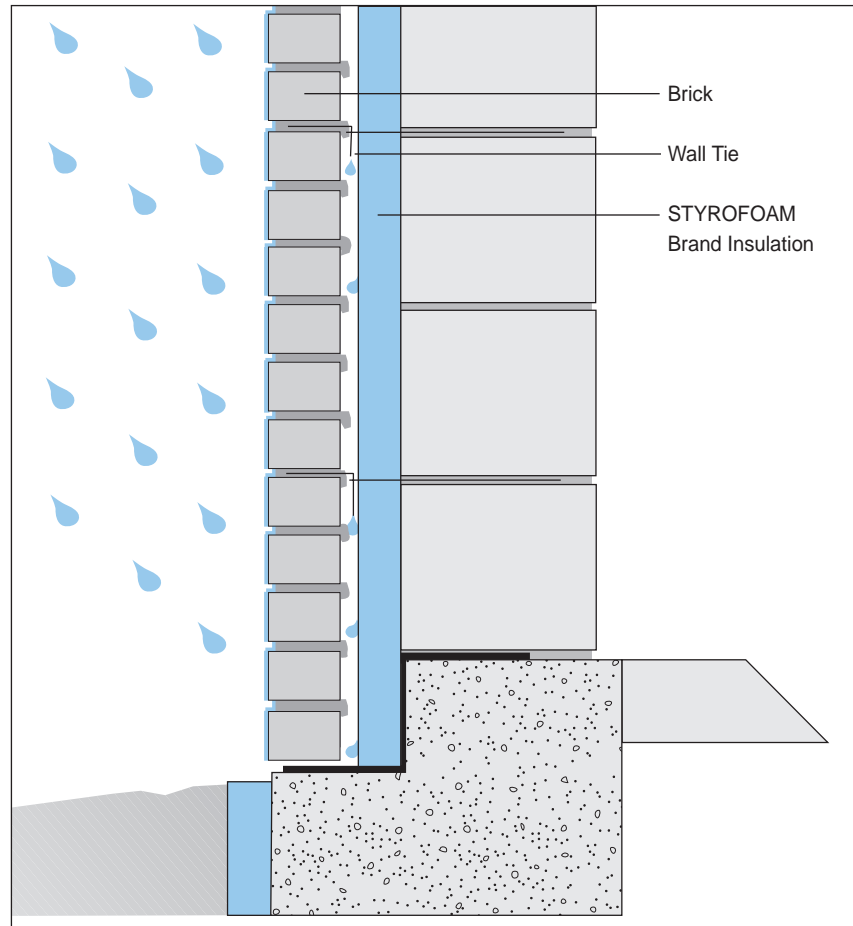

Given the fact that moisture will enter the wall cavity, the importance of properly designed flashings and weepholes is well understood. However, equally important is that the materials used in the construction of the wall must be resistant to moisture and corrosion. Bricks must be freeze/thaw resistant, and the flashing materials and brick ties must be

corrosion resistant. With all the consideration given to moisture in the design of the cavity wall, **shouldn't equal consideration be given to the moisture resistance of the insulation?** It doesn't make much sense to use an insulation with less than superior moisture resistance since, if it fails, the insulation can't be easily replaced.

STYROFOAM Brand Insulation is Moisture Resistant

The moisture resistance of STYROFOAM* brand insulation **far surpasses** that of all other types of insulations including foil-faced polyisocyanurates. STYROFOAM brand insulation is recommended for severe moisture environments. The following is a list of a few of the severe moisture environments in which STYROFOAM brand insulation has demonstrated a long, successful history:

- Flotation billets for boat docks and swim rafts
- Roof insulation for above membrane use in protected membrane roof systems and plaza decks
- Soil insulation for beneath roadways and airport runways
- Pipe insulation for underground water lines
- Foundation wall and slab insulation for the below grade perimeter of buildings
- Floating pond covers for hot, anaerobic waste treatment ponds

In each of these applications, STYROFOAM brand insulation is constantly exposed to moisture and freeze/thaw action. Even under these severe conditions, it continues to show excellent long-term performance. In fact, most designers would never consider using foil-faced polyisocyanurates in these applications.

STYROFOAM Brand Insulation Approved for Severe Moisture Environments

The U.S. Army Corps of Engineers Cold Regions Research & Engineering Lab (CRREL) has conducted testing of insulations in protected membrane roofs. It has concluded that, due to the severe moisture conditions on these roofs, the only acceptable insulation is extruded polystyrene, such as STYROFOAM brand insulation.²

The State of Alaska has also investigated the use of STYROFOAM brand insulation and polyurethane/polyisocyanurate foams as insulations beneath roadways and airfields in Alaska. Based on their findings, STYROFOAM brand insulation has been approved by the Alaska Department of Transportation for use beneath roadways and airfields. However, due to the “high moisture absorption” of polyurethane/polyisocyanurate foams, these products “are not presently accepted by the Alaska Department of Transportation for use beneath roads or airfields.”³

Polyiso’s Require Protection from Moisture

Foil-faced polyisocyanurates do not have nearly the moisture resistance of STYROFOAM brand insulation. Most polyisocyanurate manufacturers require that their products be stored on pallets elevated above any standing water on the floor or the ground. If the product is stored outside, it should be covered completely by a waterproof tarpaulin. How can the foam be protected from moisture in a wall cavity?

Another polyisocyanurate manufacturer claims that its product can be used below grade on a foundation wall because the foil facer provides superior protection from water vapor. However, the manufacturer still requires the bottom edge of the foam and all the foam joints to be covered with tape. Then a protection course, such as a fiberboard, is required to prevent damage to the foil during backfilling. Are these same precautions taken in a wall cavity? ASHRAE also states that deterioration of the foil facer can occur due to contact with wet cement mortar.

Reflective R-Values Virtually Impossible To Achieve

Another claim made by some polyisocyanurate manufacturers is that an additional R – 2.77 can be

achieved by the reflective foil facer in a cavity airspace. The basis for this claim is the 1989 ASHRAE Fundamentals Handbook. ASHRAE does allow an R-value of 2.77 for an air space with a bright foil facer on one side. An airspace with no foil facer has an R-value of only 0.94. Therefore, the foil-faced polyisocyanurate has an advantage of 1.83 Rs, right?

Wrong! Have you ever noticed that these airspace R-values are always called “design” R-values? The reason is that reflective R-values are difficult, if not impossible, to achieve in real world installations. The following statement regarding reflective airspaces is made by the ASHRAE Handbook: “Values apply for ideal conditions, i.e., airspaces of uniform thickness bounded by plane, smooth, parallel surfaces with no air leakage to or from the space. When accurate values are required, use overall U-factors determined through calibrated hot box (ASTM C 976) or guarded hot box (ASTM C 236) testing.”⁴

If you’ve ever looked at the back side of a brick wall you know it is anything but perfectly uniform and smooth because of the mortar which pushes out of the backside of the joint (see the picture on the front page). We actually measured the R-value of a wall cavity with a foil-faced insulation using a guarded hot box (ASTM C 236). The results⁵ showed that the difference between a foil-faced insulation and a nonfoil-faced product was only 0.2 Rs, and we purposely kept the foil clean and bright. We also closed off the weepholes to prevent air leakage into the cavity. In a normal installation, with rough walls, with mortar smears on the foil, and with air moving in through the weepholes, it’s doubtful that any R-value difference actually occurs.

NRCA Recommends a 5.6 R-Value for Polyiso's

The final argument relates to the R-value claim of 5.0 per inch for STYROFOAM brand insulation and 7.2 per inch for most foil-faced polyisocyanurates. Studies have shown that foil-faced polyisocyanurates can lose 20-30% of their R-value when simply stored at room temperature for one year. A study by Dynatech R/D Company found that the R-value of a 1.5" foil-faced polyisocyanurate fell to 5.33 per inch and the R-value of a 3.0" foil-faced polyisocyanurate fell to 5.63 per inch over a 360 day period. STYROFOAM aged for this same time period showed no R-value loss.⁶ As a result of this and other studies, the National Roofing Contractors Association (NRCA) has recommended that designers use an R-value of 5.6 for estimating the long-term performance of polyisocyanurates.⁷ The bottom line is that, although their literature-claimed R-values were significantly different, the R-values of STYROFOAM brand insulation and foil-faced polyisocyanurates were almost identical after one year. And this study didn't even consider the possibility of the insulation getting wet.

have ozone depletion potentials over 90% less than standard CFC blowing agents.

- Block and brick wall cavities must be designed to accommodate the moisture which will enter the cavity.
- Designers ensure that moisture-resistant structural materials are used in wall cavities.
- They should also ensure that moisture-resistant insulation is used – – STYROFOAM.

While it may be tempting to use foil-faced polyisocyanurates in a block and brick wall cavity because of the promise of higher R-values, we think that, when you consider all of the facts, the only real choice is clear ...

STYROFOAM Brand Insulation is the best long-term value for Cavity Walls.

Summary

When considering which insulation to use in a cavity wall construction, remember the following points:

- While foil-faced polyisocyanurates do have higher initial R-values, studies have shown that the aged R-values of these products are similar to that of STYROFOAM brand insulation.
- Dow backs up the R-value of STYROFOAM brand insulation by providing a 15-year limited R-value warranty.
- The reflective R-value claim of 2.77 is virtually impossible to achieve in a block and brick cavity wall.
- STYROFOAM brand insulation is also CFC-free. It is manufactured with HCFC blowing agents which

¹ "Exterior Wall Construction in High-Rise Buildings - Masonry Cavity Walls and Veneers on Frame Buildings", J.W. Sawers, Canada Mortgage and Housing Corporation, NHA 5450 81/12, Ottawa, Ontario.

² "Wetting of Polystyrene and Urethane Roof Insulations in the Laboratory and on a Protected Membrane Roof", Wayne Tobiasson, et al, U.S. Army Corps of Engineers Cold Regions Research and Engineering Laboratory, Paper presented at ASTM Committee C16 Conference on Thermal Insulation, Materials and Systems, 26 December 1984, Dallas, TX.

³ "Insulation Performance Beneath Roads and Airfields in Alaska", David Esch, Highway Research Manager, Alaska Dept. of Transportation and Public Facilities. Paper presented at the Proceedings of the Fourth International Cold Regions Engineering Specialty Conference, Anchorage, AK, 1986.

⁴ 1989 ASHRAE Handbook Fundamentals, American Society of Heating, Refrigerating and Air Conditioning Engineers, Inc., Atlanta, GA, pg 22.3.

⁵ "Thermal Resistances of Insulated Brick Veneer Walls with Reflective and Nonreflective Air Spaces," A.G. Contreras and A.J. Palfey, Thermal Insulation, Materials, and Systems for Energy Conservation in the '80s, ASTM STP 789, American Society for Testing and Materials, 1083, pp. 373-383.

⁶ "Experimental Methods for Determining the Thermal Performance of Cellular Plastic Insulation Materials Used in Roofs", Desjarlais and Tye, Dynatech Scientific, Inc., 8th Conference on Roofing Technology, Gaithersburg, MD., April 16-17, 1987

⁷ "In-Service R-values (ISR) for Polyisocyanurate and Polyurethane Roof Insulation Boards", Joint Technical Bulletin, November 1987, National Roofing Contractors Association and Midwest Roofing Contractors Association.

Notice: No freedom from any patent owned by Seller or others is to be inferred. Because use conditions and applicable laws may differ from one location to another and may change with time, Customer is responsible for determining whether products and the information in this document are appropriate for Customer's use and for ensuring that Customer's workplace and disposal practices are in compliance with applicable laws and other governmental enactments. Seller assumes no obligation or liability for the information in this document. NO WARRANTIES ARE GIVEN; ALL IMPLIED WARRANTIES OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE ARE EXPRESSLY EXCLUDED.

Notice: STYROFOAM brand insulation is **combustible** and should be protected from flame and other high heat sources. It should be installed with code-acceptable thermal barriers or used in approved alternative constructions. For more information, contact Dow (1-800-441-4DOW).

Published May 1996.



For Technical Information:
1-800-441-4DOW (4369)

The Dow Chemical Company
Construction Materials Group
200 Larkin Center
Midland, MI 48674
Visit our website: www.styrofoam.com

For Sales Information:
1-800-232-2436



*Trademark of The Dow Chemical Company.

Form No. 179-4283-596QRP